

The secrets of a 14th century wall painting in the Western Himalayas: Structural damage sheds light onto the painting technique in the Tsuglag-khang in Kanji in Ladakh



Alexandra Skedzuhn, Martina Oeter, Christine Bläuer, Christian Luczanits



Fig. 1 Kanji village, with the Tsuglag-khang located to the left of the river, source: Christian Luczanits 2003

The remote village of Kanji is situated on a cross point of three valleys at an altitude of 3,875 meters in the Kargil district of the Ladakh region in Jammu and Kashmir State of India. One of the village's most remarkable structures is the Tsuglag-khang (gTsug-lag-khang), with 700-years old wall paintings and sculptures. Until today, this art-historical treasure is largely unknown in professional circles.

Over the centuries, more and more layers of earthen material have been put onto the temple roof and have

led to major structural problems within the earthen architecture. After the structural conservation works were carried out by the Achi Association, the organisation could address the conservation of the wall paintings and sculptures.

The secco paintings, typical for the region and the period, mainly depict mandalas. Damaged areas caused by infiltrating water allowed for a profound insight into the painting process which an investigation of an undamaged wall painting would not have been able to confer.



Fig. 2 Tsuglag-khang before conservation, source: Christian Luczanits 2000

Other findings were obtained by inspecting the paint layer with different methods of illumination and by microscopic investigations. In addition to the investigation on site, the painting support, the medium and the pigments were analysed in two laboratories in Switzerland, the Expert Center in Zurich and at the Conservation Science Consulting CSC Sàrl in Fribourg.

This paper summarises and assesses the results of our research and aims at providing an insight into the sophisticated artistic working process of 14th century wall paintings in the Western Himalaya.

Introduction

Kanji is a small village in the Kargil district of the Ladakh region which belongs to the Indian State Jammu and Kashmir. It can be accessed through a small river valley from the village Heniskot which is located along the Srinagar-Kargil-Leh highway. The village is situated

on a cross point of three valleys at an altitude of 3.875 m and has about twenty families who farm the immediate area. The historic core of the village is placed on an impressive cliff looking over the valley (Fig. 1).

Approaching from the village and passing the mani walls and stupas the view opens towards the small single room structure of the Tsuglag-khang. Local tradition attributes this temple to the great translator Rinchen Zangpo (Rin-chen-bzang-po: 958–1055). Instead, the temple is approximately 700 years old and presumably dates from the period when Kanji was part of a local kingdom ruled from Wanla.

The temple lies on an eastward slope. This critical position of the gompa, namely on an inclination, in combination with the immense overload onto the roof in the course of several centuries, with additions of earthen material during each of these maintenance measures, have caused severe static problems to the building.

The Tsuglag-khang is a Drikung Kagyü temple and for generations has been used and taken care of by



Fig. 3 The throne platform with clay sculptures, source: Christian Luczanits 2003

one of the village families. 30 to 40 years ago the family addressed the static challenges by building a battered stone facing around the base of the temple. Then, in 1996, two external buttresses were built on the lower side of the slope with the help of Lamayuru monastery. Although these measures stopped further outward movement of the walls, the wall paintings had suffered severe damage as a consequence of the ingress of water resulting from these static problems. The instability of the walls caused cracks, and water seeping through the roof soiled and partly destroyed the paintings. In agreement with the caretaker family and the Drikung Kagyü Order, the Achi Association⁷ began with the conservation on the temple (Fig. 2).

After the structural conservation, the works concentrated on the conservation and cleaning of the wall paintings. Large areas of the paintings could be cleaned from earthen surface deposits and dirt, but in many areas the wall paintings are irreversibly lost due to water ingress and the subsequent washing out of the water

sensitive murals and plaster. The damaged paintings, on the other hand, provided the opportunity to investigate the various stages of the painting process which would have otherwise – with an intact paint layer – not been visible.

Description of the Temple

The temple is a cubic, one-room structure of about five to five metres with a flat roof and an entrance porch on its south side. The porch is formed with the extension of the lateral walls of the temple towards the south, and has a central pillar with a crudely carved capital. The most distinctive elements of the roof structure are the two brick-string courses resting on cantilevered willow sticks, which lie on three sides of the structure at roof-level. This building detail might indicate a former second roof. This presumption was supported by the caretaker of the temple who had told us that during the lifetime of his father, there used to be an additional roof

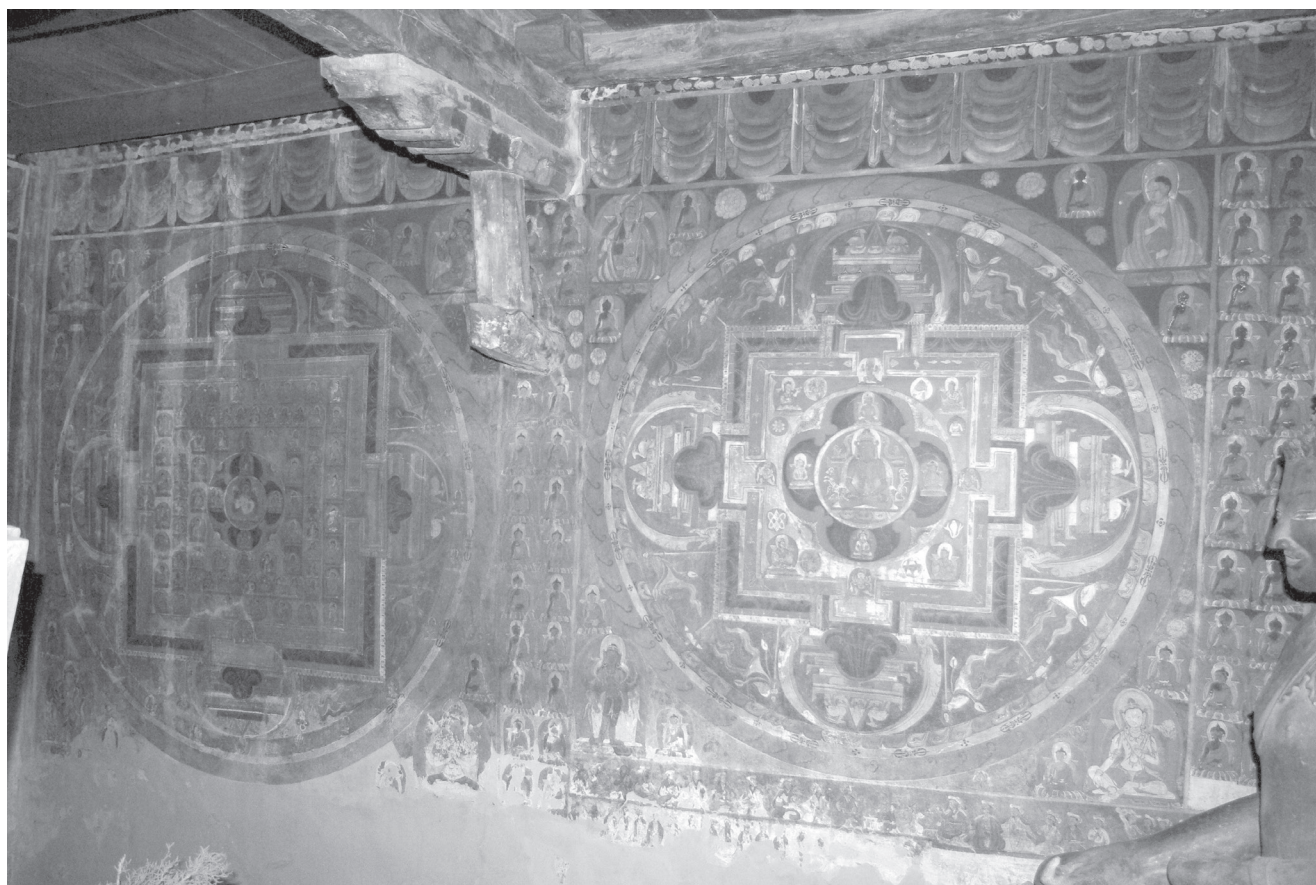


Fig. 4 East wall after conservation and cleaning, source: Martina Oeter 2010

on the temple which had been removed approximately 50 years ago to provide wood for another, more recent temple.²

The supporting structure of the building is made of river stones which serve as foundation. Adobe bricks are laid on top of this foundation covered on the exterior and interior by earthen plaster. The brick walls are 75 cm thick, equalling one and a half bricks. The only opening of the small temple is the doorway in the south, which provides little light for the interior. Opposite the entrance along the back or north wall three larger than life size sculptures are seated on lotus thrones side by side on a common throne platform, while the wall behind them and all the remaining walls are painted.

The three large polychrome clay sculptures depict the four-armed Bodhisattva Six-syllable Avalokiteshvara (Ṣaḍakṣara Lokeśvara; Chenrezik Yigedrugpa/sPyan-ras-gzigs Yi-ge-drug-pa in Tibetan) in the centre, flanked by the Medicine Buddha (Bhaiṣajyaguru; Menla/

sMan-bla) and the goddess Green Tara (Śyamatārā; Dölma Changu/Grol-ma ljang-gu; Fig. 3).

Behind the sculptures, the north wall is covered with the painted throne backs, and on the upper edge of the wall there is a teaching lineage providing the only clue in terms of age and school affiliation. As can be recognised from the figures at the beginning of the row in the upper left corner, this is a lineage of a Kagyü (bKa'-brgyud) branch of Tibetan Buddhism. The lineage starts in the top left corner with the primordial Buddha ('ādibuddha') Vajradhara. Seven figures of this lineage – including the great Indian adepts ('mahāsiddha') Tilopa and Naropa, and the Tibetan teachers Marpa, Milarepa, Gampopa and Phagmodrupa – are represented above the Medicine Buddha and seven more not individualized teachers continue this lineage above a depiction of Green Tara. The lineage does not give a decisive clue to the branch of the Kagyü School referred to here, but the total number of teachers depicted exceeds the most

common depiction in the Wanla Avalokiteshvara temple by one person and suggests an early 14th century date for the Kanji depictions.

The pillar in the centre of the room supports the main east-west beam. This beam visually divides the room into a southern and a northern half. The brackets supporting the beam also divide the side walls into halves, each of them filled with a large mandala. Thus, each side wall has a southern and a northern mandala depiction (Fig. 4). Corresponding with this layout there are also two mandalas to the right and left of the entrance doorway separated by the door, and a central representation above the door frame.

Wall Paintings

The painted surfaces are structured by dark yellow lines, and the top and bottom of the painted surfaces are decorated with common border motifs. At the top a row of geese and a valance motif representing a hanging cloth are used. At the bottom the painted area is demarcated by another common border motive, the so-called lozenge pattern actually representing a row of stylized and differently coloured pearls.

The west or left wall is dominated by two mandalas each covering half of the wall (Fig. 4). The space between them and underneath the main beam features repeated depictions of Buddha Akshobhya (Akṣobhya; Mikyöpa/Mi-bskyod-pa) in rows of two. To the left is a mandala with the Bodhisattva Vajrasattva in the centre of a four-petaled circle surrounded by four squares. As the presence of the Pratyekabuddhas and hearers (monks) within the mandala palace indicates, this is a variant of the main mandala of the ritual cycle 'eliminating all unfavourable rebirths' (Sarvadurgatipariśodhana). The corners outside the mandala are occupied by four central deities. Most significant among them is an unusual form of the goddess Sarasvati (Sarasvatī; Yangchenma/dbYangs-can-ma) in the upper right corner, blue and holding a sword and a book, the only other depiction of which is found at Wanla.³

The right side mandala is dedicated to the Buddha of long life, Amitayus (Amitāyus; Tsepakme/Tshedpag-med). This 13-deity mandala only consists of the central four-petaled lotus in a circle and the palace. Among the four main figures outside the mandala are the mythical teacher Padmasambhava in the top

left corner (Fig. 12), and a teacher wearing Indian monastic dress under the cape in the upper right corner. Again, it appears that this mandala is unique, but it can be related to the cycle to 'eliminating all unfavourable rebirths', as this also features a mandala of the King of Long Life (his full name being Aparimitāyuhpunya-jñānasambhāratejorāja). In addition, the association of Amitayus with Padmasambhava is known from other sites in the region as well, in particular the main niche of the Avalokiteshvara temple in Wanla.

Below the mandala a part of an extensive donor assembly is preserved. The top row features a drinking feast attended only by the male and a traditional row dance in which four turbaned men lead five women, the last one a girl. Women are seated underneath the men in the second row, and there is also a fragmentary remain of the vessels holding 'chang', the traditional alcoholic beverage.

The composition on the east or right side wall mirrors the one of the left with two mandalas taking most of the space and repeated representations of Buddha Akshobhya between them. Here, the north eastern or left mandala is centred on the teaching Buddha Shakyamuni (Śākyamuni; Shakya Thubpa/Śākya-thubpa) dressed in monastic robes and bejewelled seated within an eight-petaled lotus. This is the Shakyamuni or Shakyasimha (Śākyasimha; Shakya Senge/Śākya-seng-ge) mandala of the ritual cycle 'eliminating all unfavourable rebirths', and its iconography largely conforms with its most frequent representation.⁴ At earlier sites, such as Nako and Alchi, this has been the only mandala represented from this cycle and thus was considered representative of it. In the corners around the mandala circle are an unusual three-headed and two-armed form of the Bodhisattva Avalokiteshvara,⁵ two red standing Bodhisattvas representing a rare form of the Bodhisattva and future Buddha Maitreya, and an eleven-headed, 22-armed form of Avalokiteshvara.

Underneath the mandala is a long inscription panel that begins in front of the platform for the sculptures and ends to the left of the eleven-headed Avalokiteshvara. On the other side of this Bodhisattva begins a depiction of the life of the Buddha with the first scene showing the Bodhisattva teaching the gods in Tushita (*Tuṣita*) Heaven. This narrative frieze continues along this and the entry walls, and may also have covered the bottom of the left part of the south wall.



Fig. 5 Paleolake 'moonland' near Lamayuru, one of the main areas where 'markalak' can be quarried, source: Verena Knippel 2006

The badly damaged second mandala on this wall is centred on the four-faced meditating Vairocana. Outside the mandala circle, and iconographically part of it are the unfavourable states of rebirth, the hells in the lower left, the hungry ghosts in the upper left, the animals in the upper right and the demi-gods ('asura') fighting the gods ('deva') in the lower right corner. A Bodhisattva sits in the hell, and a female dressed in local West Tibetan style is shown in the realm of the hungry ghosts. This is the main mandala of the 'eliminating all unfavourable rebirths' cycle. Also the entry wall features two main mandalas, here placed to the sides of the door. In general the wall is in fairly poor condition with large sections damaged by water ingress. What has been painted above the door, presumably a seated, four-armed form of the protector Mahakala (*Mahākāla*)

and attendant deities, is practically completely lost with only the row of riders to his right partly preserved. The life of the Buddha scenes once represented at the bottom of this wall are also extremely fragmentary.

Through the cleaning of that wall, the left mandala can now be recognized as a seventeen-deity Vajrapani (*Vajrapāṇi*; *Chakna Dorje/Phyag-na-rdo-rje*) mandala, his entourage consisting of four Bodhisattvas, eight offering goddesses and four gate-keepers. Around the mandala are again repeated representations of Buddha Akshobhya, the Buddha of the eastern direction. Underneath the mandala a larger now lost Buddha occupies the centre of two rows of Buddhas. A strip underneath these Buddhas probably once showed dancing goddesses paralleling the composition on the other side of the entrance.

The mandala to the right of the door is somewhat better preserved and likely dedicated to a wrathful form of Vajrapani. In the circle surrounding him are twelve fierce deities, approximately half of them preserved. In the corners are the four inner offering goddesses, and four gate-keepers occupy the doors. This mandala is surrounded by repeated representations of Buddha Amitabha, the Buddha of the western direction. At the bottom are two rows of the same Buddha flanking a larger central one. The lotus on which the central Buddha is sitting is flanked by six goddesses each playing musical instruments and/or dancing.

The represented mandalas are only in part familiar as several of them have not been identified elsewhere in exactly the same form. Nevertheless, all the mandalas can be associated with those found in commentaries to the 'eliminating all unfavourable rebirths' (Durgatipariśodhana) cycle. The base tantras of this cycle and school and time specific commentaries to it have to be considered the main source of Kanji's iconographic program. Although some iconographic motives are shared with Wanla's Avalokiteshvara temple, the Kanji paintings are surprisingly distinctive from that temple, even though it must be historically rather close. The longer lineage, the simpler representation of Padmasambhava, and the more distinctly commentarial iconography, among others, indicate a later date for the Kanji temple.

The Painting Technology⁶

The supporting structure of the wall paintings is a multilayer earthen plaster. The coarse ground layer of the plaster consists of clay, sand and gravel (grain size between 0.1 and 2.0 cm), straw or other plant fibres and animal hair. The thickness of this plaster varies between three and five centimetres. These materials most probably were collected in the vicinity of the site. The top, fine plaster layer is very thin, measuring approximately only 0.1 cm. It is made of very fine clay known in Ladakh by the name of 'markalak' which translates to butter mud.

Different scientific investigations of 'markalak' samples characterise it as a mixture of abundant quantities of 50–80% clay, the effective binder of the plaster, 7–40% silt that usually contains some calcium carbonate (in the form of calcite sometimes together with aragonite) and no or only a few percent of sand grains (Nicolaescu and

Alexander 2008, p. 62; Alexander and Catanese 2007, p. 35; Jägers and Jägers 2003, p. 3). 'Markalak' can be quarried in various deposits all over Ladakh. Two major sources of clay materials with excellent working properties can be found at 'moonland' near Lamayuru (Fig. 5), and near Spituk, which both formed as paleolake deposits (Phartiyal et al. 2005, p. 254).



Fig. 6 Detail of a wall painting with missing paint layer, the white ground has become visible, source: Alexandra Skedzuhn 2011

The plaster was smoothened with a smooth hard tool, possibly a river stone or a conch shell to obtain an even painting ground.⁷ Then the paintings were applied onto dry walls, using the pigments dispersed in an organic binder, a technique known as *secco* painting. In preparation for the painting the surface was covered with a white prime coating only approx. 0.1 mm thin, made out of a fibrous mineral material (Figs. 6 and 14).

According to our analysis this seems to be the same material which was used for the white washes on the façades, the so called 'karsi'. The analysed white ground layers of the paintings as well as the historic 'karsi' of the façade were exclusively composed of serpentine minerals (probably antigorite) and calcium carbonates.

We believe that these minerals have mainly been selected because of their fibrous structure, which gives the material a wonderful silvery shine.⁸ Until now it was impossible to establish where exactly these materials had been collected, but they can be found in the immediate regional geology, (Steck 2003, compilation of

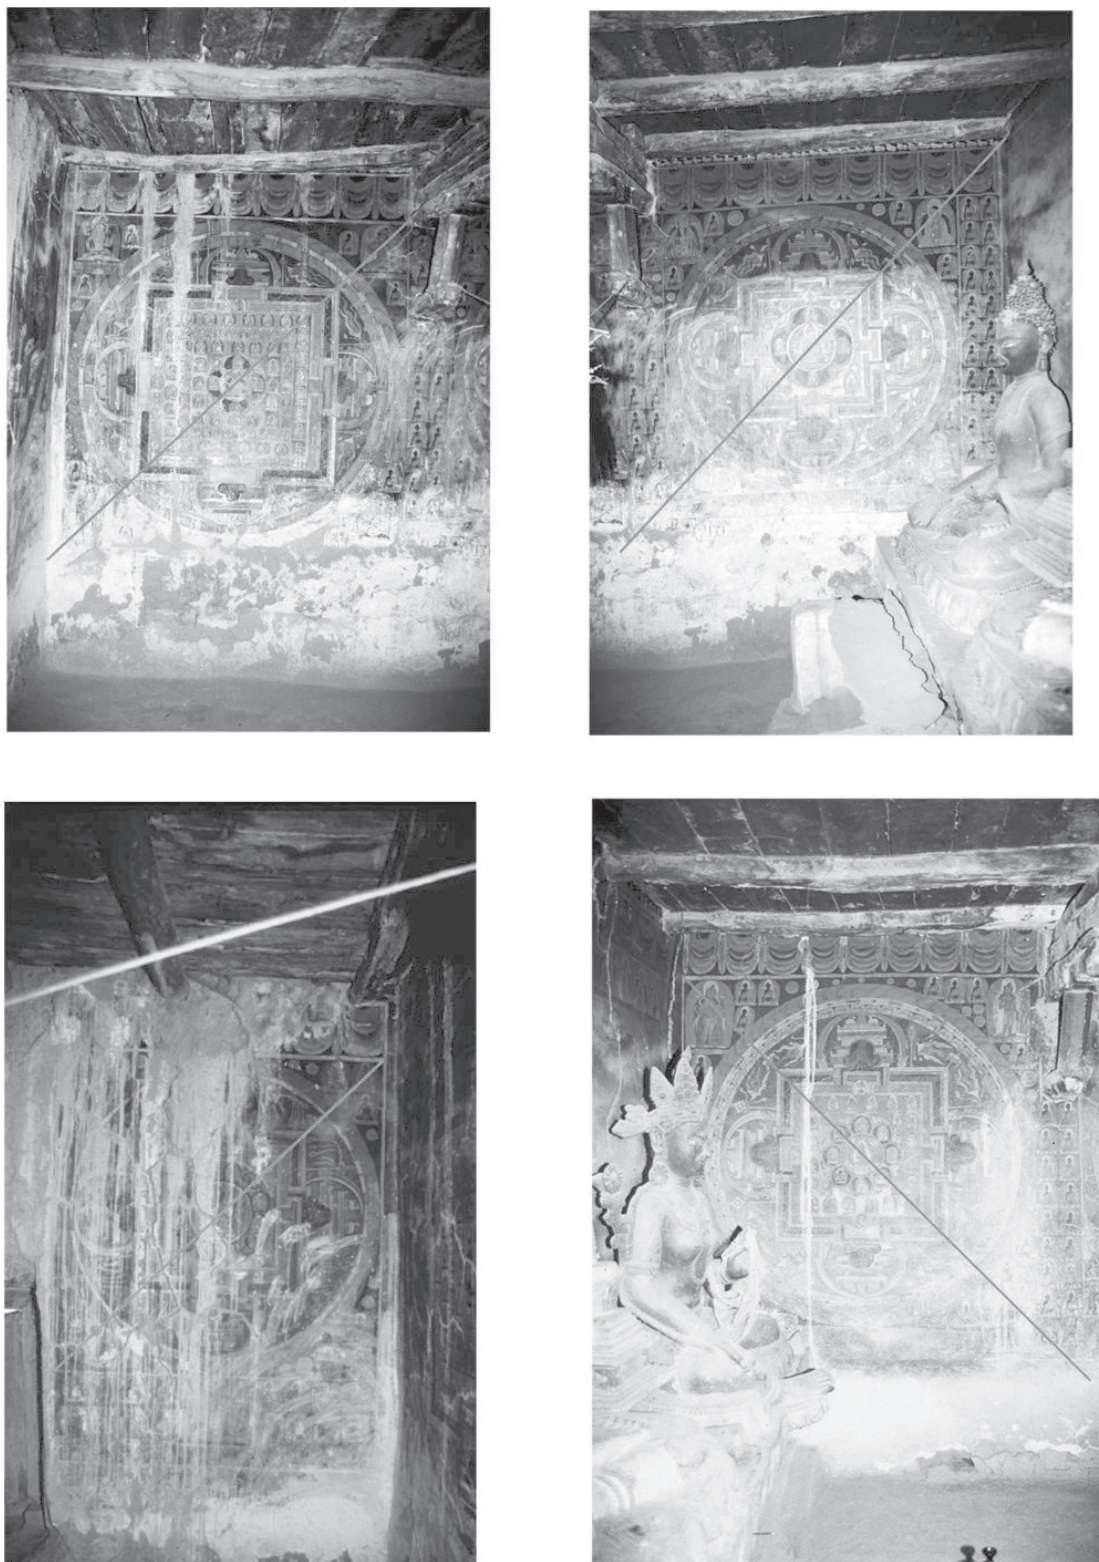


Fig. 7 The mandala on the top right is located in the north section of the west wall, while the mandala on the bottom right lies on the opposite side, on the north section of the east wall. The diagonals show the different geometrical layouts. Source of photo: Christian Luczanits 2000, source of graphics: Steven Post 2003



Fig. 8 Major construction lines can be detected underneath the paint layer, see arrows. Source: Christian Luczanits 2000

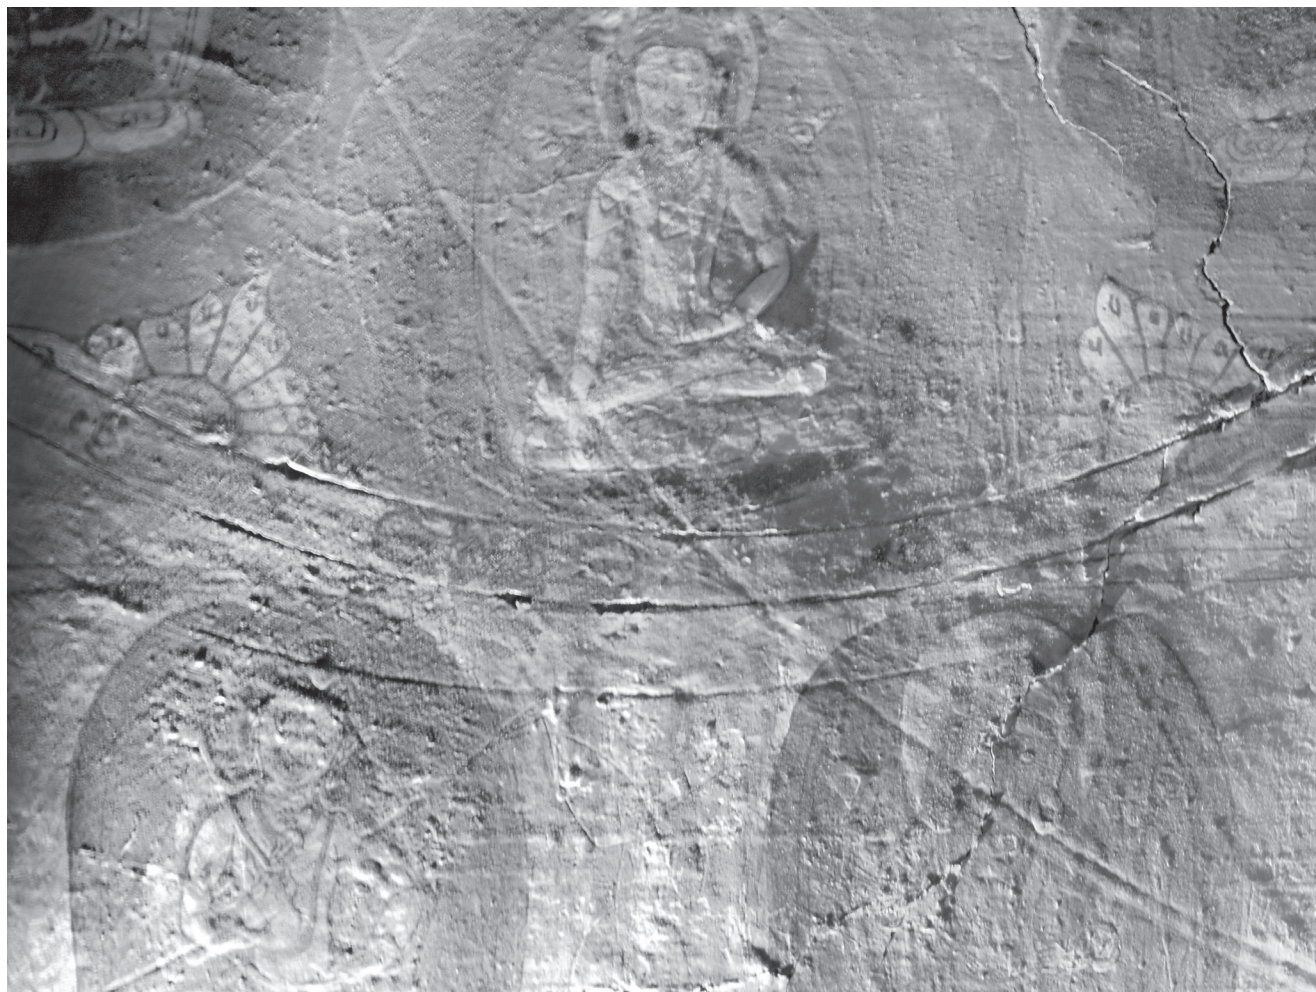


Fig. 9 Mandala incisions, north section of the east wall, source: Alexandra Skedzuhn 2010

the geological map of NW Himalaya, Plate I) and in fact, locals have told us that 'karsi' can be found within a few hours walking distance from Kanji.

So far it is not clear if the prime coating ('karsi') was applied with or without a binder. Generally, it appears that the properties of the specific type of 'karsi' material determine the necessity whether a binder needs to be added: If the 'karsi' adheres well to the support, and if it has a low capillarity and thus does not require a sizing to reduce its absorbency, no binder is necessary.

Only traces of organic material could be analysed in the prime coating in the Tsuglag-khang.⁹ We suppose that they could be the remains of a purification process for the preparation of 'karsi'. Locals have told us that a type of 'karsi' is mixed with milk during the preparation. Alternatively, the presence of the organic material in the primer could indicate the use of a binder. Whether the

binder was mixed into the 'karsi', and/or applied in a second step onto the 'karsi' layer as a sizing, or even penetrated into the 'karsi' layer when the colour was painted onto the surface cannot be determined with certainty.¹⁰

After the white primer had been applied, the walls were geometrically divided into different sections. This was carried out according to the iconometric rules. Here, the layout of the Tsuglag-khang determined a first division of the entrance and the two side walls into six more or less equal rectangles each featuring a mandala.

According to the painting tradition, the artist then laid down the main orientation lines for the mandalas. There are a total of eight major lines for each mandala, starting with the two diagonals, followed by the vertical, the horizontal and the four outer border lines (Jackson and Jackson 2006, p. 45). Presumably this work



Fig. 10 Construction lines in red colour, south section of the east wall, source: Martina Oeter 2011

commenced with the mandala on the northern half of the west wall. Only here the diagonal cutting through the mandala reaches the top right corner of the wall. All diagonals of the other mandalas end below the valance motif. This signifies that with this mandala the width of the upper border zone had been established (Fig. 6). The construction work of the other mandalas was then apparently carried out afterwards (Fig. 8, see arrows).

These major lines presumably were executed as painted lines ('lönthik'/rlon-thig for wet lines) with a marking string (Jackson and Jackson 2006, p. 45), as can be seen in the mandala at the southern half of the west wall; using strong direct light onto the painting, the horizontal line can be detected underneath the paint layer.

To determine these major lines, but also to construct the mandala circles, a compass ('korthik'/skor-thig) was used for small circles and a so-called 'korpang' (skor-pang) for large circles (Jackson and Jackson, 2006, p. 46). Many circle incisions can be detected when observing the mandalas with ranking light. Interestingly, every mandala has

different incisions which might be an indication for more than one painter working in the temple or for different construction methods and iconometric requirements depending on the type of mandala (Fig. 8).

This conforms to the fact that in early mandala depictions each of the mandalas has its distinctive iconometry depending on the mandala elements being represented and the basic geometry of the mandala, in particular the relationship of the outer circles to the palace and its gates and the interior of the palace structure. For example, the two mandalas on the left wall are highly distinctive, as the Vajrapani mandala on the left has essentially four concentric assemblies of deities, and thus a much larger palace than the Amitayus mandala, which only has a single circle of deities.

As the next step the walls were geometrically divided with a grid of exactly positioned lines ('thikhang'/thig-khang; Jackson and Jackson 2006, p. 49). These vertical and horizontal lines are typical for the geometric division of the walls to establish the proportions of all



Fig. 11 Underdrawing visible on the top rider, compared with the bottom figure which has a thinner outline, located in the centre of the south wall, source: Alexandra Skedzuhn 2011

sacred images according to iconometric rules. This is especially visible on the southern mandala on the east wall where a large section of the upper layer of the wall painting is lost due to water infiltration. The visible red lines show the so called finger units, as they correspond to the width of a finger¹¹ (Fig. 9).

Deities were proportionally structured according to strict canonical rules. Historic texts on iconometry say that if an artist did not act in alignment with these rules, this would have a negative impact on himself resulting in illness, or unfavourable rebirth, and on his environment causing suffering or failing harvests (Henss 2006, p. 112). As a next step, precise sketches were made, at least for the detailed figures.

Some of these sketches are visible in heavily damaged areas of the wall paintings. A good example is visible on the south wall above the door, where these under-drawings of horses and riders were carried out in a reddish brown colour with relatively broad outlines (Fig. 10).

The palette of pigments found so far in the paint layers is rich (Küng 2010a, p. 1) and corresponds to the investigations in other temples of that period.

According to the Tibetan-Buddhist painting tradition, the materials were not only employed depending on availability and physical properties, but also on their connection to the religious image. Precious pigments such as azurite are understood as having outstanding merit (Griesser 2008, p. 37). Also the use of different binders according to the religious significance is reported by local thangka painters¹² even though the confirmation of the use of different binders in the Kanji Tsuglag-khang seems to be connected more to technical considerations.

The underdrawings most probably were executed by the master in a freehand manner. His task was also to colour code the images. Two different systems can be used, namely to code an area with corresponding numbers or with the abbreviation of a colour. And again, damaged areas could reveal the coding system in the Tsuglag-khang in Kanji: The Tibetan word for white, *dkar*, can be found in several sections, as well as the abbreviation for yellow, *ser*¹³ (Fig. 11).

Another painting principle was to begin the painting with the distant planes of colour within the composition before painting those in the front, to obtain sharper edges of the more important details (Jackson

and Jackson 2006, p. 96). These distant planes or backgrounds in the Tsuglag-khang are painted in red (cinnabar) directly onto the white primer (Küng 2010a, p. 1) whereas the dark blue areas consist of a bottom black paint layer and top layer of azurite (Küng 2010a, p. 2; Bläuer 2013, p. 2). The images and many important details in the foreground were given various coloured under-paintings. There are several reasons why this may have been done. One reason may be that specific pigments are less opaque than others and require thus a paint basis with a stronger covering power. An example for this would be the costly, usually coarsely ground blue pigment azurite, which is often found to be painted on top of a layer of black paint (Fig. 14).

Another reason is that by applying different colours on top of each other, specific optical effects can be achieved such as a glazing effect, lending the image a translucent appearance. Usually this technique, called shading or tinting, was done by applying darker shading washes over a lighter base colour (Jackson and Jackson 2006, p. 97) (Fig. 13).

According to painting tradition, the main shading colours were organic dyes and lakes (Jackson and Jackson 2006, p. 112). This corresponds to the use of pigments and colours in the Kanji temple.

In accordance, each colour of the wall paintings in the Tsuglag-khang, usually has its own colour of under-painting, with only some exceptions. The analyses made during a field campaign by Andreas Küng revealed the following results: The drab ochre coloured details have a bright yellow under-painting (rather coarsely grained orpiment), the dark blue-green areas (indigo and orpiment) a bright green one (mixture of orpiment and little indigo), and the dusky pink details (red lac) usually an orange one (cinnabar and vegetable black on orpiment). Traditional guidelines also influenced which elements of the painting were to be endowed with contour lines. Specific details could thus be emphasised making them stand out compared to other less important ones. Also minute details for instance necklaces, fabric design or facial details were painted (Jackson and Jackson 2006, p. 129).

The analyses in situ and in laboratory have revealed the use of different materials, as described in the following. The dark blue paint layers are about 0.1 mm thick and formed by very coarse azurite (up to 50 microns in grain size) and coarse red to orange ochre.¹⁴ It sits on



Fig. 12 Colour coding indicating the abbreviation of the colour white, source: Alexandra Skedzuhn 2011



Fig. 13 Detail of painting: washes in blue and pink over a lighter base colour, source: Alexandra Skedzuhn 2011

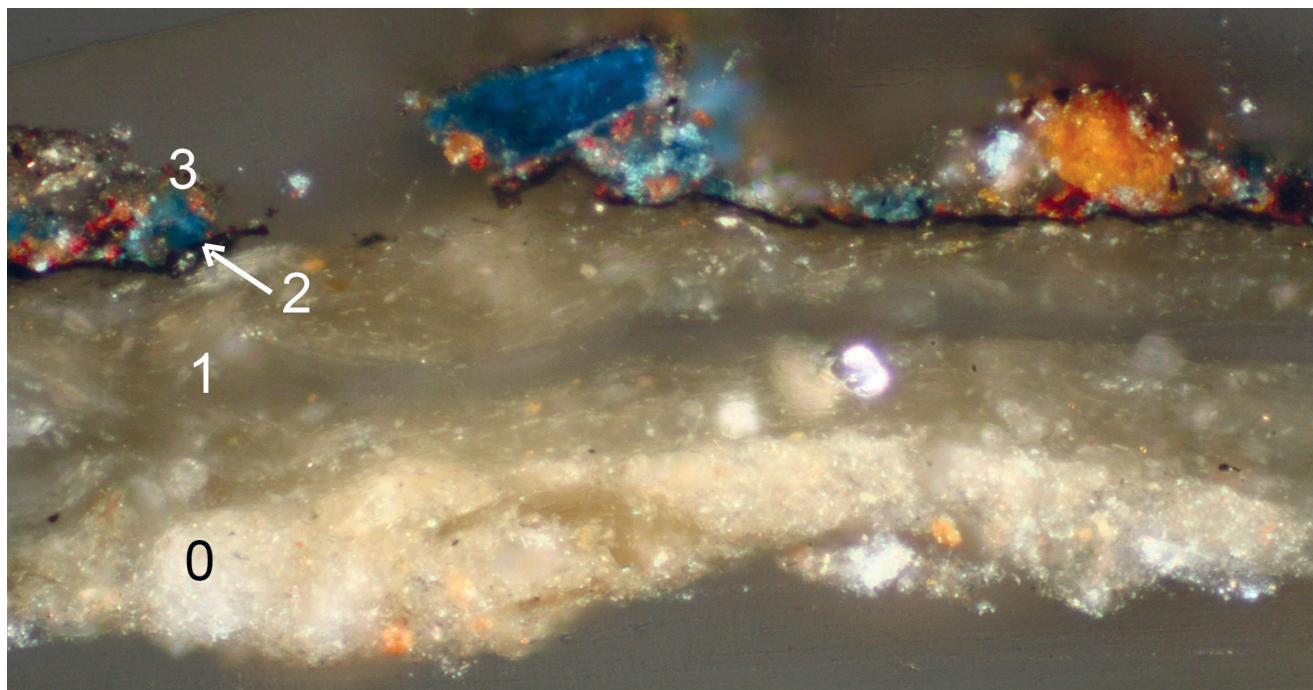


Fig. 14 Cross section through the paint layers in a dark blue area; 0: plaster surface, 1: prime coating (karsi form serpentine minerals), 2: black underpaint, 3: scarce remains of blue paint layer with coarse azurite and red ochre; image width 440 μ m, source: Christine Bläuer 2012

a very thin (about 2 to 10 microns) layer of black that could not be identified with certainty. From microscopic analysis and micro-chemical testing it appears to be a charcoal black (Fig. 14).

That the azurite blue was admixed with red ochre at first appears unusual, but might be explained by considering the principles of chromatics. When the paintings were executed the artists would have worked in a warm open flame light, which renders thus blue colours slightly green. To compensate this effect, its complimentary colour red would have lessened the effect and obtained a somewhat purer blue. The binding media which is soluble in cold water is according to our micro-chemical testing and FTIR measurements most likely a gum.¹⁵

The dark red paint layer which is made of cinnabar with little ochre is only about 20 microns thin (Fig. 15).

The binding medium consists according to micro-chemical testing and FTIR spectroscopy of a distemper. This means that a water based and oil based binder were mixed together. Oils could derive from either walnuts, poppy seeds, linseed or sunflowers, or egg yolk. Water based binder could be either size, or gums

made of fruit trees or roots or egg white. Further analysis however is required to establish more precisely what kind of distemper was used for the paintings in Kanji.

As mentioned above, the reason for different binders could lie in religious motivated effects of specific materials, or apparently, in the case of cinnabar, painting technology.

Cinnabar may become black within water-based binders, for instance gum or size.¹⁶ Applied in a distemper binder and subsequently protected by a varnish such as a madder lake, as literature suggests, this would not happen (Kremer 2013a).

More pink shades of red are painted using red lake which has not yet been fully attributed, sometimes mixes with some charcoal black and little yellow ochre (Küng 2010a, p. 3).¹⁷ The translucent dusky pink which was used for modelling and shading painting details is made of organic red dyes with minor admixtures of charcoal black (Küng 2010a, p. 12).

The yellow colours are obtained with the mineral orpiment, which is often mixed together with some orange red ochre (Küng 2010a, p. 1).

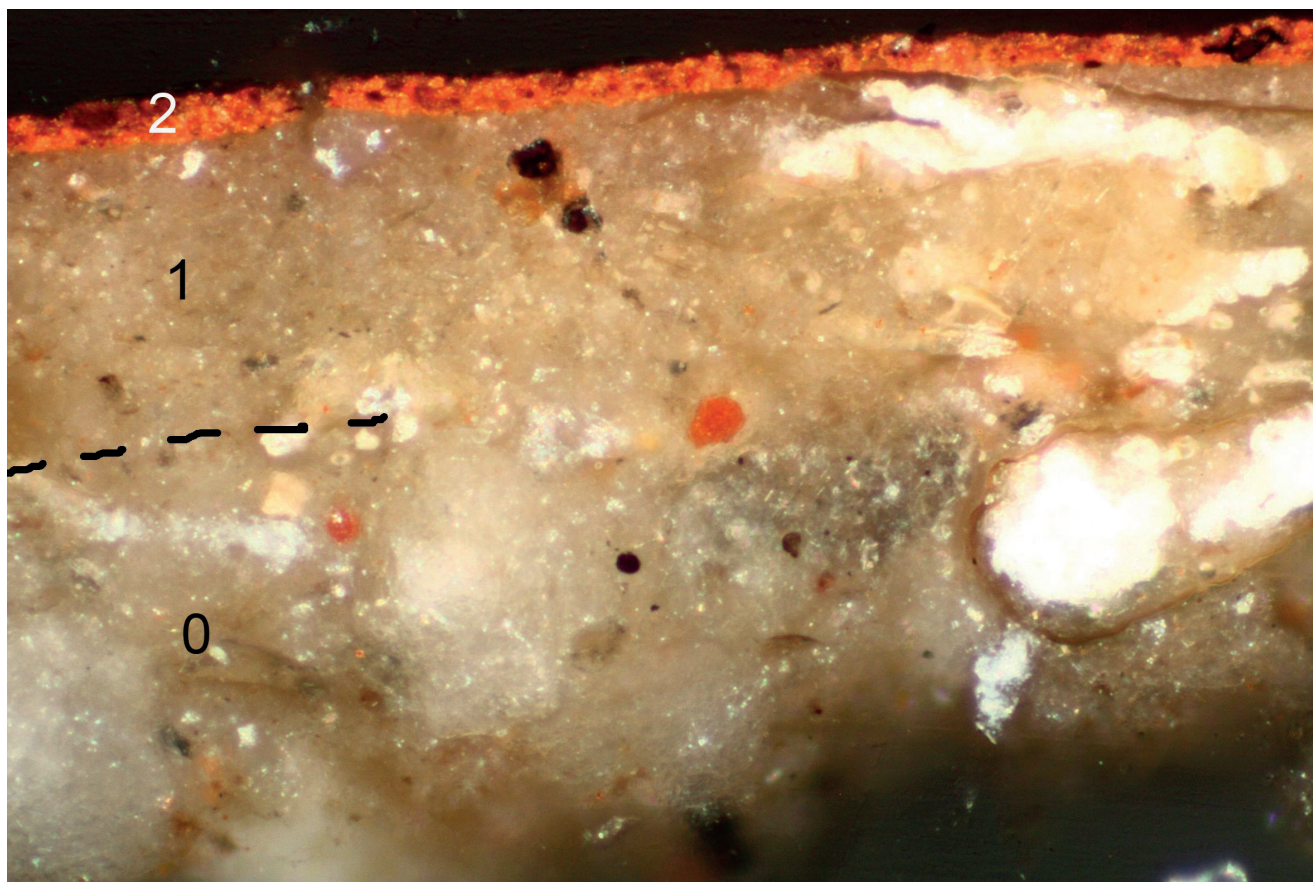


Fig. 15 Cross section through the paint layer in a dark red area; 0: plaster surface, 1: prime coating (serpentine minerals with calcite as well as aragonite), 2: red paint layer made of cinnabar; image width 440 μm , source: Christine Bläuer 2012

The green colour in all of the analysed samples turned out to be a mixture of orpiment and indigo, sometimes mixed with charcoal black, but it never consists of a sole green pigment (Küng 2010a, p. 6). The darker, more olive shade of green is made of charcoal black, very fine yellow and red ochre, and blue dyestuff (Küng 2010a, p. 12).

A mixture of an blue colorant – most likely indigo blue – with orpiment to obtain a green colour has also been found in the analysed samples of green colour taken at the Avalokiteshvara temple in Wanla (Küng 2010b, p. 6) and the Lhakhang Gongma in Nako (Bogin 2005, p. 212). The pigment malachite so far has only been found in later paintings of this region, although it is from its mineralogy very similar to azurite and the two minerals often occur together in nature.

For the black colour, agglomerates of a finely grained black substance can be observed as well as coarser grained charcoal black (Küng 2010a, p. 7).

Traditionally, paintings are concluded with a ceremony, which brings a divinity to life. This is known as the eye-opening act and is inherent part of the consecration of a painting or a temple (Jackson and Jackson 2006, p. 139).

Concluding Remarks

The investigations of the paintings in the Tsuglagkhang reveal how close the painters adhered to the ancient Indian and Tibetan painting technology described in the historic sources.

Additionally, our investigations have brought forth several relevant aspects pertaining to the causes of damages and the conservation of the paintings.

Foremost are the material aspects of the support, primer, and paint layer with its pigments and different binders. According to the type of pigment and binder employed for the painting, the paint layers react very



Fig. 16 Orpiment underpainting visible due to water infiltration which has washed away the overlying ochre, source: Steven Post 2006

differently to the very same external factors, be it damaging forces or a conservation treatment. In areas with an orpiment under-painting for example, the flaky structure of the mineral grains does not allow for a very strong adherence to overlying paint so that the top paint layer easily washed off during rainwater infiltration (Fig. 16).

For conservators working on these paintings it is further important to know that orpiment contains arsenic and thus is highly toxic; extra care and safety is extremely important. Another interesting example is the use of azurite for the light blue painting details. The pigment was admixed with an aqueous binder, which most probably was done to highlight best the beauty of this coarsely grained blue stone mineral, with

its comparatively low reflective indices. Soot adheres more easily to a rough surface than to a smooth one, resulting in heavily blackened paint layer. The details of the blue Bodhisattva faces are often hardly visible, but as the binder is soluble already in cold water, the details painted with azurite need even more care during a cleaning process than other details painted with a distemper.

Apart from these technical considerations, there are more complex questions pertaining the conservation of the paintings.

There might arise the dilemma in the approach of how to conserve wall paintings: either focussing on state-of-the-art conservation products, or according to the religious connotation of the painting materials.

Does the use of 'wrong' products lessen the religious strength and value of an image?

Apart from these technical considerations, there are more complex questions pertaining to the conservation of the paintings. How much needs to be conserved for religious reasons and what is merely an aesthetic choice? What is the religious strength and value of a depiction or an image and how is it affected by conservation?

Does the religious environment require additional ceremonies (pujas) besides the de-consecration and re-consecration of the main image to maintain the integrity of the religious environment?

Opinions diverge greatly on these matters, but the knowledge we have acquired through our on-site investigations, literary research and discussions with Tibetan Buddhist clergy and local thangka painters, have helped us to evaluate the conservation process from very different perspectives making us aware of how necessary it is to integrate the various stakeholders and disciplines into the decision making process and to assess conservation within its different contexts.

Bibliography

- ALEXANDER**, André & Andreas **CATANESE**, 2007: "The Leh Old Town, Conservation Project, Ladakh, Indian Himalayas", *E-conservation* 1:29–50, available at: <http://www.e-conservationline.com/content/view/567/155/> (accessed: 3.4.2010)
- BLÄUER**, Christine, 2013: *Kanji, Tsuglag-khang, Analysis of Samples from the Wall Paintings, Sampling 2010 and 2011*, unpublished report, Zürich: Archive of the Achi Association, 1–9
- BIGIN**, Stephanie, 2005: "A Technical Study of the Early Buddhist Wall Paintings at Nako, Himachal Pradesh, India", *Kunsttechnologie und Konservierung* 19, (2): Worms, 199–229
- CHAKRABARTI**, Jayanta, 1980: *Techniques in Indian Mural Paintings*, Calcutta (K P Bagchi & Company)
- COOMARASWAMY**, Ananda K., 1934: "The Technique and Theory of Indian Painting", *Technical Studies in the Field of Fine Arts* 3, Cambridge, 59–89
- DASSER**, Karl Ludwig, 1996: "Some Observations on the Technology of the Wall Paintings in the Sumtsek", *Alchi, Ladakh's Hidden Buddhist Sanctuary, The Sumtsek*, London (Serindia Publications) 273–276
- GRIESSER**, Ute, 2009: "Presenting, Handling and Treating Sacred Thangkas According to Western Standards and Respecting their Cultural Context—An Achievable Common Purpose?", *Proceedings of the Forum on the Conservation of Thangkas*, special session of the ICOM-CC 15th Triennial Conference, New Delhi, India, September 26, 2008, 30–43
- HENSS**, Michael, 2006: „Vom rechten Maß und richtiger Zahl – Ikonometrie in der buddhistischen Kunst Tibets“, *Tibet, Klöster öffnen ihre Schatzkammern*, Kulturstiftung Ruhr Essen (ed.), exhibition catalogue, München (Hirmer) 105–113
- ISTUDOR**, Ioan & Anca **DINĂ** & Geanina **ROȘU** & Doina **ȘECLĂMAN** & Gheorghe **NICULESCU**, December 2007: "An Alteration Phenomenon of Cinnabar Red Pigment in the Mural Paintings from Sucevita", *E-conservation* 2/2007, available online at: <http://www.e-conservation-line.com/content/view/253/77/> (accessed: 25.3.2013)
- JACKSON**, David P. & Janice A. **JACKSON**, 2006: *Tibetan Thangka Painting, Methods and Materials*, Hong Kong (Serindia Publications)
- JÄGERS**, Elisabeth & Erhard **JÄGERS**, 2003: *Dokumentation der Proben*, unpublished analyses, Zürich, archive of the Achi Association
- KREMER** Pigmente, 2013a: *Zinnober, Cinnabrit, aus der Hunan Provinz, China*, available online at <http://kremer-pigmente.de/10620.htm> (accessed: 11.3.2013)
- KREMER** Pigmente, 2013b: *Azurit, Bergblau, basisches Kupfercarbonat blau, Pigment Blue 30*, available online at <http://kremer-pigmente.de/10200.htm> (accessed: 14.3.2013)
- KÜNG**, Andreas 2010a: *Kanji-Tempel, Proben 2005: Untersuchungsresultate – Dokumentation der Entnahmestellen*, unpublished analyses, Zürich, archive of the Achi Association
- KÜNG**, Andreas, 2010b: *Wanla-Tempel, Proben 2005 und 2006: Untersuchungsresultate – Dokumentation der Entnahmestellen*, unpublished analyses, Zürich, archive of the Achi Association
- LO BUE**, Erberto, 2006: „Tibetische Malerei“, *Tibet, Klöster öffnen ihre Schatzkammern*, Kulturstiftung Ruhr Essen (ed.), exhibition catalogue, München (Hirmer) 90–95
- NICOLAESCU**, Anca & André **ALEXANDER**, 2008: „Red Maitreya Temple–Leh, Ladakh“, *E-conservation* 6, Mural Conservation Project, A Tibet Heritage Fund Program, September 2008:56–77, available at: <http://www.e-conservationline.com/content/view/500/100/> (accessed: 26.8.2011)
- OETER**, Martina, 2003: *Paintings and Sculpture—Work Techniques*, available online at <http://www.achias-sociation.org/activities-sites-kanji-tsuglag-khang-report-paintings-and-sculpture-work-techniques.php> (accessed: 22.3.2013)
- PHARTIYAL**, Binita & Sharma **ANUPAM** & Rajeev **UPADHYAY** & **RAM-AWATAR** & Anshu K. **SINHA**, 2005: "Quaternary Geology, Tectonics and Distribution of Palaeo- and Present Fluvio/Glacio Lacustrine Deposits in Ladakh, NW Indian Himalaya – A Study Based on Field Observations", *Geomorphology* 65, Amsterdam 241–256
- SKORUPSKI**, Tadeusz, 1983: *The Sarvadurgatipariśodhana Tantra, Elimination of all Evil Destinies*, New Delhi-Varanasi-Patna (Motilal Banarsidass)
- STECK**, Albrecht, 2003: "Geology of the NW Indian Himalaya", *Eclogae geol. Helv.* 96, Cham, 147–196

Notes

- 1 The Achi Association (www.achiassociation.org), an NGO based in India and Europe, is working in the Western Himalayas for the preservation of Ladakh's cultural heritage. An interdisciplinary team of specialists from India and Europe, partly linked to academic programs at different universities, combines in-depth research with hands-on preservation.
- 2 A large flat stone which might have functioned as a footing for an upper pillar was found above the central pillar when the roof was renewed. This supports the presumption that there used to be an upper, second roof in former times.
- 3 In Wanla this goddess is represented in the upper section of the left side wall of the Maitreya niche in the Avalokiteshvara Temple.
- 4 For descriptions see Skorupski 1983, pp. 35–42, which in other places also describes the other mandalas referred to later in the text.
- 5 Would it not be for the vase as the second object, this image could easily be recognised as Avalokiteshvara Chintamanichakra (Avalokiteśvara Cintāmaṇicakra; Chenrezi Yizhin-khorlo/sPyan-ras-gzigs yid-bzhin 'khor-lo), who is commonly depicted in exactly the same posture. However, it would be curious if the name giving attribute, the wheel ('cakra'), is replaced by a vase.
- 6 For the identification of the paint layer and the prime coating microscopic and micro-chemical methods were used as well as infrared spectroscopy. For the investigation of the fine layer of earthen plaster, additionally grain size analyses by sedimentation and sieving were employed. Some of the analyses were performed on site by Andreas Küng (Küng 2010a) during the 2005 field work campaign (dispersions analysed using a polarizing field microscope).
- 7 Jackson and Jackson mention thangkas to be smoothed with these tools (Jackson and Jackson 2006, p. 21).
- 8 The primer employed for the Lotsawa Lhakhang in Nako contains some mica, and Bogin presumes the reason lies in the optical effect of it, as it would increase the luminosity of the paint layer (Bogin 2005, p. 207).
- 9 Investigation carried out by FTIR spectroscopy (Bläuer 2013, p. 2).
- 10 In comparison, analyses undertaken for the Sumtsek in Alchi showed that the primer contains a binder of proteins and starch (Dasser 1996, p. 274). Our analysis (FTIR and micro-chemical testing) of the primer on wall paintings in the Avalokiteshvara temple in Wanla showed that both the calcium carbonate (calcite or aragonite) and the gypsum primers contain proteins.
- 11 Names of other measurement units are also derived from the human body, such as the face measure, or the palm measure (Jackson and Jackson 2006, p. 50), see also Lo Bue 2006, p. 94.
- 12 We were informed by thangka painters that the use of animal glue is employed for fierce deities as it lends them more strength, whereas the compassionate deities are painted with a binder deriving from plants, such as gum or sap.
- 13 We are thankful to the thangka painter Tsewang Stanzin who had pointed out the colour codes. This coding system is mentioned in literature on painting technology, such as Jackson and Jackson 2006, p. 91, or Coomaraswamy 1934, p. 74.
- 14 Analyses using polarized light microscopy on cross sections and dispersions.
- 15 Kremer 2013b: Azurite according to Kremer should be used either as an egg distemper or mixed with an abundant quantity of size or gum.
- 16 This could occur with UV radiation, see Istudor et al. 2007, pp. 24–33.
- 17 The black colour is most probably charcoal black, but this still has to be confirmed.

earth construction & tradition

Hubert Feiglstorfer

vol 2

IVA–ICRA

Institute for Comparative Research in Architecture

Vienna 2018

This book is a compilation of articles related to the topic 'earth construction and tradition'.

Picture rights and sources used:

All contributions and source references are the responsibility of the authors. The rights to the photos and other graphic material are held by the respective photographers listed or by the institutions listed in the source references. All sources were carefully researched and named where possible. Should a source attribution have been omitted this will be rectified in the next edition and the correct source added. Pictures with a low resolution are depicted just in the case of their particular cultural value and that no equivalent picture was available.

Feiglstorfer, Hubert (editor)

earth construction and tradition – vol 2

Print:

Buchdrucker, Druck und Graphikservice GmbH, Hardegasse 69, A-1220 Vienna, www.buchdrucker.at

Copyright:

IVA–ICRA, Institute for Comparative Research in Architecture, Vienna 2018

ISBN 978-3-900265-37-3

Under the patronage of ISCEAH / ICOMOS

International Scientific Committee on Earthen Architectural Heritage



ICOMOS - ISCEAH
International Scientific Committee
on Earthen Architectural Heritage

**International Council on
Monuments and Sites**

Supported by:

- Stadt Wien, Kulturabteilung MA 7 is the main sponsor and supported this publication with 1000 €
- TU Wien: Department for History of Architecture and Building Archaeology
- University of Natural Resources and Life Sciences, Vienna: Institute of Applied Geology (IAG)
- Bundesdenkmalamt, Österreich (BDA)
- Museumsdorf Niedersulz - Kultur. Region. Niederösterreich
- Skanzen Strážnice, Czech Republic
- Architectural Heritage, Development and Future (AHDF)
- Citizen Science Project - Earth construction in the Weinviertel region
- National Heritage Institute, Czech Republic (NHI)
- Association for the Renewal of the Village and the Small Town, Czech Republic



TABLE OF CONTENTS

	Preface
9	Editorial
11–19	List of authors
20	Architectural History
	Roland Meingast
	Hubert Feiglstorfer
21–83	Earth building history in eastern Austria
	Jochen Georg Güntzel
85–104	Von dem Bau der sogenannten Lehm- oder Wellerwände, dem ‚Schillerhaus‘ in Gohlis und einer publizistischen Verschwörung die Wellerwände betreffend
	Ivana Žabičková
	Jan Růžička
105–121	Earth Construction in the Czech Republic
	Hauke Haupts
123–130	The workman houses at Koengen in Oslo
	Georgi Georgiev
131–140	Earthen architecture in Bulgaria
	Ileana Mavrodin
141–149	Tradition and modern cob structures in Romania
	Vincent Laureau
151–166	When a nomadic tradition meets the city – Mutations of the Bozoian constructive culture in Bamako, Mali
	Mario Lazarovich
167–187	Raw earth in the architecture of Salta, Argentina
	Hubert Feiglstorfer
189–203	Remarks on Himalayan earth roof constructions

204	Conservation
	Alexandra Skedzuhn Martina Oeter Christine Bläuer Christian Luczanits
205–222	The secrets of a 14th century wall painting in the Western Himalayas: Structural damage sheds light onto the painting technique in the Tsuglag-khang in Kanji in Ladakh
223–233	Sandeep Kumar Preventive conservation of wall paintings on earthen architecture – case study Mangyu in Ladakh
235–241	Shakirdzhan Pidaev Marina Reutova Ancient monuments of earthen architecture in Uzbekistan and their conservation
243–257	Mike Schnelle Daniela Geyer Grat Be'al Gəbri – a monumental half timber complex of the early 1st millennium B.C. in the Ethiopian Highland
259–269	Randolph Langenbach Ancient and modern earthen construction in an earthquake: Bam, Iran in 2003
271–279	Noora Mehraeen Recognition of the Bam citadel entrance gate and analyzing related earthquake damages
281–294	Sasha Riahi Moghaddam Regularization and revitalization of architectural, cultural and natural values on Saryazd historical village, Iran, south of Yazd
295–312	Azimeh Riahi Dehkordi On the renovation of the Friday Mosque at Abyaneh, Iran
313–337	Salma Samar Damluji A mosque & saint domes in Wadi Sah – Hadramut, Yemen
339–358	Mohammad Sharif Zami A conceptual framework by construction professionals to understand the factors influencing adoption of stabilised earth to address urban low cost housing crisis

359–371	Denise Pozzi-Escot Henry Eduardo Torres Emergency conservation at the Archaeological Sanctuary of Pachacamac – Peru
373–387	Denise Pozzi-Escot Gianella Pacheco Templo Pintado of the Pachacamac Sanctuary: Conservation and research
388	Material research
389–393	Gernot Minke Important characteristics of clay plaster: linear shrinkage, resistance against abrasion and erosion, sorption and desorption of humidity
395–420	Thomas Sturm Luís Ramos Paulo B. Lourenço Compressed earth blocks – an alternative to traditional fired bricks

Editorial

Hubert Feiglstorfer is an architect and researcher at the Institute for Social Anthropology of the Austrian Academy of Sciences in Vienna. He holds a PhD in Architectural History and a PhD in Clay Mineralogy, both related to the Himalayas.

He teaches in the field of building history and building research at the Vienna University of Technology and in the field of earth building research at the University of Natural Resources and Life Sciences in Vienna. He is member of ICOMOS-Austria (International Council on Monuments) and of the ICOMOS Executive Committee ISCEAH (International Scientific Committee on Earthen Architectural Heritage).

Earth construction and tradition is a series of publications with a wide spectrum in the field of building with earth on an international scope. The publication deals with modern and historic architecture as well and gives a certain focus on building traditions, be it in their original, developed or newly defined form. The contributions are subdivided in three groups which define the structure of the book. A focus of this volume is in the fields of architectural history, conservation and material research.

part 1 **ARCHITECTURAL HISTORY**

part 2 **CONSERVATION**

part 3 **MATERIAL RESEARCH**

LIST OF AUTHORS

Christine Bläuer

Achi Association, Switzerland; Conservation Science Consulting Sàrl in Fribourg, Switzerland

Christine Bläuer is a conservation scientist who studied geology and mineralogy and wrote her PhD 1987 on the weathering of Bernese sandstone. She then expanded her professional horizon during the collaboration as a scientist in research projects on wall painting conservation in Germany, by teaching at several universities and colleges as well as through practical activities as a conservation scientist. Her main expertise and interests are the analysis and conservation of inorganic materials (ancient pigments, mortar materials and stones), the identification of the causes of degradation (internal and external factors), passive and preventive conservation measures for monuments and sites.

blaeuer@conservation-science.ch

Salma Samar Damluji

British architect of Iraqi and Lebanese origin. She graduated from the Architectural Association School of Architecture and The Royal College of Art in London where she did her PhD on the *Mud Brick Architecture of Hadramut*. She worked with Egyptian Architect Hassan Fathy in Cairo in the 1970s and 1980s. In 2007 she established with colleagues in Yemen *The Daw'an Architecture Foundation* based in Mukalla, Hadramut that is responsible for carrying out several projects of earth construction and rehabilitation there. See www.dawanarchitecturefoundation.org. Damluji has carried out extensive field work and design research on vernacular architecture across the Middle East, Arabia and North Africa. She is author of several publications, and was *Elected Foreign Member of the French Academy for Architecture*, 2017. She received the Silver Medal of the Académie d'Architecture, Restoration Award, Paris 2015 and The Global Award for Sustainable Architecture, Paris 2012.

ssdamluji@aub.edu.lb

Hubert Feiglstorfer

Austrian Academy of Sciences; Vienna University of Technology; Vienna University of Natural Resources and Life Sciences

Hubert Feiglstorfer is an architect and researcher at the Institute for Social Anthropology (ISA) of the Austrian Academy of Sciences in Vienna (ÖAW). He holds a PhD in Architectural History and a PhD in Clay Mineralogy, both related to the Himalayas. He also teaches in the field of building history and building research at the Vienna University of Technology and in the field of earth architecture at the University of Natural Resources and Life Sciences in Vienna. He is member of ICOMOS-Austria (International Council on Monuments) and of ISCEAH (International Scientific Committee on Earthen Architectural Heritage).

hubert.feiglstorfer@gmail.com

Georgi Stefanov Georgiev

He is an architect with 20 years of experience in earthen architecture. He is the author of the e-book *Building with Natural Materials*, which is available as free download. He presented posters and papers at the TERRA 2000 8th International Conference of Earthen Architecture, Devon, England, at Earth USA 2011 and Earth USA 2013, New Mexico, USA. He published in newspapers and magazines in Bulgaria and designed and realized public and private buildings in earth.

e-mail: ultrajoro@abv.bg

Daniela Geyer

Werkart Restaurierung GbR

She degreed 2007 in Potsdam, at the University of Applied Sciences. Her diploma thesis was about: *Comparative testing of grouts made of soil for conservation of earthen architecture*. Since 2000 freelance conservation and partner of werkart Restaurierung. Her regional projects and international cooperations are i.a. *Cung An Dinh Palace in Hue, Vietnam* - Vice-Project Manager, Restorer with the Leibniz Society Berlin and GCREP, promoted by the Federal Foreign Office Berlin; Surveying of loan art objects and condition reports for a Russian, Sudanese and Turkish exhibition in Abu Dhabi, for KDC, Dr. Stefan Simon and the Abu Dhabi authority; Restoration work at the *Grat Be'al Gebri* in Yeha, Ethiopia, in collaboration with the Sanaa Branch of the DAI, German archaeological Institute.

geyer@werkart-restaurierung.de

Jochen Georg Güntzel

University of Applied Sciences in Detmold, Schule für Architektur und Innenarchitektur der Hochschule Ostwestfalen-Lippe (OWL)

He studied architecture at the Technical University of Aachen (master thesis) and worked as a freelance architect before continuing as a professor at university. He was Teaching Assistant at the School of Architecture at the University of Oregon and professor for the subjects of designing public buildings and building construction at the Fachhochschule Lippe, today Hochschule Ostwestfalen-Lippe. In 1986 he finished his doctoral thesis *Zur Geschichte des Lehmbaus in Deutschland* at the University of Kassel. Several publications on the history of earth building as well as on the architect, urban planner and headmaster Hermann Cuno Heufer, on the revival of timber construction in historicism, on the painter and architectural draftsman Karl Junker, on the elementary teacher and poet Friedrich Frevert and on the conductor, orchestral entrepreneur and composer Benjamin Bilse. He was invited as speaker and plenary speaker to several international conferences.

pressestelle@hs-owl.de

Hauke Haupts

He is an architect with research interests in historical earthen construction especially in thermal conditions. He is voting member for earthen architectural heritage at ICOMOS Norway. He works as a monument conservator at the regional historic monuments protection authority in Trøndelag state administration in Norway.

haupts27@msn.com

Vincent Laureau

Ecole Nationale Supérieure d'Architecture de Paris-Val de Seine (ENSAPVS), Laboratoire Centre de Recherche sur l'Habitat (CRH), LAVUE UMR 7218 CNRS

Vincent Laureau is Architect d.p.l.g. (ENSA Normandie, 2005). After graduating, he worked in different architectural offices in Paris. Then he resumed his studies in order to become an architectural teacher. He now holds a Master Degree in Geography (GECKO-Université Paris-Ouest Nanterre la Défense, 2008) and a Doctorate in Urban Planning and Spatial Planning entitled *La ville et la terre, apprendre de Bamako. Le cas de Bozobuguni un quartier autoconstruit* at Laboratory Mosaïques-LAVUE, Université Paris-Ouest Nanterre la Défense (2014). He is now a teacher at ENSA Paris-Val de Seine as a Master Assistant in Theories and Practices of Architectural and Urban Design (TPCAU). He is also a member of the CRH-LAVUE laboratory. archimotive@hotmail.com

Randolph Langenbach

Senior Analyst (Retired) at Federal Emergency Management Agency (FEMA); now an international consultant in building conservation as Conservationtech Consulting, Oakland, California, U.S.A.

Upon moving to California for an assistant professorship at the U.C. Berkeley, Langenbach, informed by his earlier work documenting historic masonry and timber textile mills, questioned the assumptions that his masonry buildings are likely to collapse in earthquakes. He then embarked on research and documentation of seismically resistant traditional construction which over the past 35 years has taken him to Kashmir, Haiti, Iran, Afghanistan, Turkey, Portugal, Italy, and Nepal. This research led to his appointment at FEMA, and the award of a Rome Prize at the American Academy in Rome. His work with earthen construction was expanded in particular after his participation in a UNESCO mission to Iran after the 2003 Bam earthquake. RL@conservationtech.com, www.conservationtech.com

Christian Luczanits

David L. Snellgrove Senior Lecturer in Tibetan and Buddhist Art, School of Oriental and African Studies, University of London

His research focuses on Buddhist art of India and Tibet. He has extensively published on Gandharan, Western Himalayan and early Tibetan art and architecture and curated a number of exhibitions. He also was teaching at the University of Vienna, UC Berkeley, Free University in Berlin, UC Santa Barbara, and Stanford University. Before joining SOAS, he was Senior Curator at the Rubin Museum of Art, New York. cl46@soas.ac.uk

Sandeep Kumar

He has a master degree in chemistry. Soon after a course in *Conservation of Paintings* at the National Museum conservation laboratory in New Delhi he joined the Indian National Trust for Art and Cultural Heritage New Delhi in 2006 and worked as senior art conservator till 2013. During this time he supervised several campaigns on conservation of Buddhist wall paintings on earthen architecture in Ladakh. He is associated with the Achi Association also as wall painting conservator and performs on different sites in Ladakh. Presently he is involved in a conservation project of South Indian traditional paintings in Delhi. bisht.sn@gmail.com

Mario Lazarovich

Salta Province Government; Salta National University; San Juan National University; San Pablo Bolivian Catholic University

He graduated at the National University of Architecture and Urbanism of Tucuman, Argentina. He is specialised in Cultural Heritage Conservation; post-graduated in Argentina (FAU-UNT, 1984), Italia (ICCROM-UNESCO, 1991–1992) and Cuba (CENCREM-La Habana, 1996). He was the Cultural Heritage General Director of the Salta Province between 1995 and 1999 and between 2007 and 2010. Since 2013, he is member of the Board of the National Commission of Monuments, Places and Historical Sites. Nowadays, he works in the Cultural Heritage Subsecretary of Salta Province Government as Professional Adviser, and in the Salta National University, the San Juan National University and the San Pablo Bolivian Catholic University (Tarija) as Guest Professor.

mario.lazarovich@gmail.com

Ileana Mavrodin

OAR (Ordinul Arhitecților Romania) The Order of Architects Romania

She is an architect specialized in earthen architecture, with 13 years experience in using clay, straw and wood to build cob and straw bale constructions in Romania. Since 2005 she is president of S.C. COB S.R.L Romania; most representative buildings are *The Fairy Tale House* in Porumbacu, a bed and breakfast in the Carpathian mountains called *Castelul de Lut din Valea Zanelor* built of cob with a shingles roof and *Popasul Verde* in Sangeorz-Bai, a holiday house built of straw bale and cob with a green roof.

ileana.mavrodin@ymail.com

Noora Mehraeen

She graduated in Conservation of Historic Building from the Art and Architecture Department, Shahid Bahonar University and continued her education as M.Sc. After Bam earthquake (2003), she cooperated in the Arg-E-Bam project as volunteer. She started teaching as lecturer at university in the field of Conservation & Historic places in 2009 and cooperated with the Cultural Heritage Organization in two field study projects on historic places in Kerman city.

noora.mehr@yahoo.com

Roland Meingast

Lopas GmbH

He is working on R&D (Research and Development) for Lopas GmbH, a company producing prefabricated Passive Houses from clay, straw and wood. He studied economic and social history at University of Vienna. Besides management of a family enterprise from 1976 on, he autodidactically studied sustainable technologies. From 1994 on, continuously parallel to development of modern commercial techniques for building with earth, he worked as a consultant on refurbishment of historic vernacular buildings, mainly on order of the building department of the Lower Austrian Government. Since then, this enabled him to study and collect data on historic vernacular earth buildings. He is also lecturer at BOKU and at Technical University of Vienna.

roland.meingast@lopas.at

Gernot Minke

University of Kassel

Gernot Minke is a retired professor of Kassel University where he headed the Research Institute of Experimental Building (Forschungslabor für Experimentelles Bauen) from 1974 onwards, and directed 50 research and development projects in the field of building with earth, building with straw bales, building with bamboo, green roofs and low-cost housing. He was invited as speaker to more than 60 international conferences and is the author of more than 300 articles and more than 20 books, among others *Building with Earth*, which was published in nine different languages, *Building with Straw* (with F. Mahlke) and *Building with Bamboo*.
minke@asl.uni-kassel.de

Martina Oeter

Achi Association, Switzerland; Otto-Friedrich-Universität Bamberg; Ostbayerische Technische Hochschule Regensburg

Martina Oeter works as a freelance conservator and head conservator of the Achi Association, and teaches at Regensburg Technical University in the Faculty of Architecture. She has studied conservation of wall paintings and stone objects at the University of Applied Sciences in Cologne, Germany and obtained her MA in Conservation Studies at the Institute of Advanced Architectural Studies, University of York, UK. The topic of her on-going doctoral thesis at Bamberg University reflects her work experience in European, African and Asian countries and the commitment to an integral approach, which combines scientific, technical and social aspects of heritage conservation.
martina_oeter@yahoo.de

Franz Ottner

Institute of Applied Geology; University of Natural Resources and Life Sciences Vienna

He is a geologist and specialised in clay mineralogy. He teaches in the fields of Applied geology, Sedimentology and Clay Mineralogy. In the last years he intensified contact to earth building scientists and concentrates his research on historical earth buildings in Austria. Particularly, material research, material quality of properties and the origin of clay and raw material in earth constructions, are important research topics.
franz.ottner@boku.ac.at

Gianella Pacheco

She is a graduate of archeology at the San Marcos University in Peru. She was responsible for research and conservation at the Templo Pintado.
gianellap1982@hotmail.com

Franz Perschl

Born in 1933; with 14 years he was trained as a bricklayer. 1961–1993 he was a judge at the court in Krems, followed by research on historical buildings in the surroundings of Krems spanning from the period of the

Roman Limes to Baroque. He specialised on reconstruction of modular measurements and layouts and on reconstruction of the patrocium of religious Christian structures by means of the orientation of the longitudinal axis towards sunrise according to the Carolingian calendar. He presented research results at the conference of the ÖGM in Vienna in 2004 and at the international conference for historical meteorology *Ordo et Mensura X* in Trier. His research is related to the fields of experimental archaeology, and the reconstruction of layouts of historical structures based on plans of post holes.

perschl@yahoo.com

Shakirdzhan Pidaev

Academy of Sciences of the Republic of Uzbekistan, Institute of Art History

He studied at the historical faculty of the Tashkent State University, has a doctoral thesis in historical sciences and is working as an archaeologist. Since 1970 he worked in the Institute of Archaeology of the Academy of Sciences of Uzbekistan. Since 2009 he works in the Institute of Art History of the Academy of Sciences of Uzbekistan where presently he is the director. He also leads bilateral expeditions with Korean archaeologists. His area of scientific interest is antique and medieval archaeology. The basic archaeological researches are carried out on the site of an ancient settlement called *Old Termez*, the historical territory of Baktrija-Toharistan, located south of Uzbekistan. He is working on the excavation of a Buddhistic complex at Karatepa including fortification works, a citadel of a site of an ancient settlement and numerous residential and craft quarters. Results of his archaeological research are monographies and about 132 published papers.

Tel.: +99871239-4278. Fax: +99871239-1771

Denise Pozzi-Escot

Museo de Sitio Pachacamac

She has a DEA degree in Archaeology and Pre-Columbian Archaeology from the University of Paris 1-Panthéon-Sorbonne. She is treasurer of ICOM Peru. She was a member of the National Technical Commission of Archaeology in the National Culture Institute of Peru. She was professor at the University of Huamanga and is professor in South American Archeology of UNT Trujillo and University of Rennes 1. Currently she is director of the Pachacamac Site Museum – Ministry of Culture of Peru.

dpozzi@cultura.gob.pe

Luís F. Ramos

University of Minho, Guimarães, Portugal, ISISE

He is assistant Professor at the ISISE, University of Minho.

iramos@civil.uminho.pt

Marina Reutova

Academy of Sciences of the Republic of Uzbekistan, Institute of Archaeology, branch of Samarkand

She studied at the chemical faculty of the Samarkand State University, has a doctoral thesis in chemical sciences and is working as chemist-conservator. Since 1977 she works in the Institute of Archaeology of the

Academy of Sciences of Uzbekistan. She absolved twice a training in France. Further more she jouned trainings in 1997 at the centre of restoration of glass, metal and ceramics in Vienne, and in 1998 at the centre of restoration of painting in Soissons. She carries out preservation and restoration of archaeological loess materials. Now she is the chief of the department of chemical-technological researches and restoration and co-director of the Uzbek-French expedition in the Institute of Archaeology of the Academy of Sciences of Uzbekistan. Her area of scientific interest are problems of preservation and restoration of archaeological adobe monuments, clay sculpture and monumental painting on clay. She is involved in the development of methods of preservation of adobe materials and their practical introduction at various archaeological monuments of Uzbekistan. A result of her research and applied work are about 84 scientific published papers.
mreutova@gmail.com

Azimeh Riahi Dehkordi

Department of Cultural Heritage in Iran

She holds an MSc in the field of architecture, restoration and rehabilitation of historical buildings and is working on her PhD at the Vienna University of Technology, Institute of History of Art, Building Archaeology and Restoration in the field of traditional earth architecture in villages in Iran with a case study in Abyaneh. She was lecturer at the Tabriz Azad University and Miras University on fundamentals of restoration of buildings and a lecturer at the Vienna University of Technology on traditional architecture in Iran. Since 1995 till present she is employed at the Cultural Heritage Organization of Iran as an expert in the field of restoration and rehabilitation of historical buildings. Between 2001 and 2009 she worked as the director of research and restoration projects in the historical village of Abyaneh, located in the centre of Iran. Now, she works as coordinator for architectural research in the historical villages of the Central Plateau of Iran.
ariahid.2010@gmail.com

Sasha Riahi Moghaddam

He graduated from the Art University of Isfahan as Master of Restoration and Rehabilitation of Architectural and Historical Fabrics. He is a researcher and lecturer in architecture and conservation with a specialisation on research and conservation of historical urban and rural architecture. Now, he is studying conservation in Tehran University in a PhD course and working at the Organization of Cultural Heritage, Handicrafts and Tourism and is deputy of Conservation Heritage in Yazd Province.
sasha.riahi@gmail.com

Jan Ruzicka

Czech Technical University in Prague, Faculty of Civil Engineering, Department of Building Structures and University Centre for Energy Efficient Buildings, Research program Architecture and the Environment;
Freelance architect at design studio KUBUS, Ltd.

He is member of the research team Architecture and the Environment at the University Centre for Energy Efficient Buildings of CTU in Prague. He focuses on mechanical physical properties of natural based materials like clay, earthen structures, straw, timber structures etc. He gained experience in several national and international research projects. He gives lectures on building structures, timber structures for passive

buildings and alternative and natural based structures at the Faculty of Civil Engineering of CTU in Prague, Department of Building Structures and he leads project studios at bachelor and master degree level. As a graduated architect he runs the design studio KUBUS, Ltd., focusing on low energy and passive buildings and ecological architecture. His aim is to bring principals of sustainability into professional life.

jan.ruzicka@fsv.cvut.cz

Mike Schnelle

Orient-Department and the Sanaa Branch of the German Archaeological Institute (DAI)

1994–2000 he studied architecture at the Technical University Berlin where 2000–2002 he finished further studies with a postgraduate master in preservation, documentation and investigation of monuments at the Department of Historical Heritage Preservation. Since 2001 till present he worked as a building historian at numerous projects of the Sanaa Branch of the German Archaeological Institute in Yemen (2001–2013) at sites like Marib, Sirwah, Tan'im and Ethiopia; 2009 up to present day at sites like Yeha, Hawelti, Wuqro. At this projects he guides architectural survey and architectural documentation and is consultant of restauration and preservation of monuments.

mike.schnelle@dainst.de

Alexandra Skedzuhn-Safir

Brandenburg University of Technology (BTU) Cottbus-Senftenberg, Germany
Achi Association, Switzerland

Alexandra Skedzuhn-Safir studied conservation of stone and ceramics in Florence, where she worked for several years. She received her BA in Conservation of Architectural Surfaces at the UAS in Hildesheim, and her MA in *World Heritage Studies* at the BTU Cottbus-Senftenberg. She has worked as conservator and instructor in Europe and Asia, and is a member of the wall painting conservation team with the Achi Association. She presently works as an academic assistant and lecturer at the BTU Cottbus-Senftenberg, where she is writing her doctoral thesis on the topography of prostitution in Florence in the 19th century. She is member of the NGO Achi Association, Zurich.

alexandra.skedzuhn@b-tu.de, a.skedzuhn@gmx.de

Thomas Sturm

University of Minho, Guimarães, Portugal, ISISE

tsturm@civil.uminho.pt

Henry Eduardo Torres

Museo de Sitio Pachacamac

He is a Civil Engineer at Ricardo Palma University in Peru. Until 2017 he worked for the Ministry of Culture as a conservator in the Pachacamac Archaeological Site Museum.

htorres@cultura.gob.pe

Ivana Žabičková

Brno University of Technology, Faculty of Architecture

Since 1988, she belongs to the academic staff of the Faculty of Architecture at the Brno University of Technology. She has taught subjects related to the load-bearing structures of buildings. She participates in research activities and is a supervisor of doctoral studies. Over the last 20 years, she has been devoted to historic earthen buildings and the use of clay in new buildings. She founded the *The Earthen Architecture Association*, of which she was chairwoman till 2016. Now, she is managing clay building courses.

zabickova@gmail.com

Mohammad Sharif Zami

King Fahd University of Petroleum and Minerals, Saudi Arabia

He is Assistant Professor of Architecture at the King Fahd University of Petroleum and Minerals, Saudi Arabia. Previously he lectured at the Harare Polytechnic, University of Zimbabwe and NUST in Zimbabwe, University of Salford in England, and UKZN in South Africa. During this period he also worked as a freelance and consultant architect with various international architectural practices. His research interests include landscape and urban design, earth construction, architectural heritage, conservation and housing. In these fields, he has published in more than 40 journals and conference papers including several book chapters. He completed a BArch degree at the Khulna University, Bangladesh, a MPhil degree at the NUST of Zimbabwe and a PhD degree at the University of Salford of England.

mdszami@kfupm.edu.sa